


TMTD masterbatch (Thiuram accelerator & sulfur donor)

- **TETRAMETHYL THIURAM DISULFIDE**
- **Molecular Weight** : **240**
- **CAS** : **137-26-8**
- **EINECS** : **205-286-2**

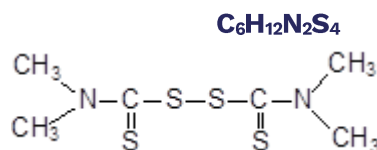

PRODUCT	Active Content (%)	Color N for Natural P for Pigment	Filtration (µm)	Mooney ML (1+4) 80°C Typical value	Density Typical value
TMTD 80 GA F140	80	Light orange* (P)	140	20	1.27

GA: Granules co-polymer of acetate/acrylate & polyethylene

* Depending on natural variation of TMTD

ACTIVE MATERIAL TYPICAL VALUES

- Initial melting point : 142 °C
- Melting point : 148 °C
- Purity : 97%

REMARKS

- Non-staining
- Non-discoloring

PROPERTIES

Mixland+[®] TMTD masterbatch is used as an ultra-accelerator or as a booster of multi-accelerator blends with thiazoles and sulfenamides, and as a vulcanization agent (sulfur donor) in most of the sulfur cured elastomers. It gives fast vulcanizations and therefore short processing times (scorchy).

It gives an excellent vulcanization plateau with good heat ageing and compression set resistance for use in sulfurless vulcanization and in EV systems. Excellent colour is obtained in carbon black-free vulcanisates.

In EPDM, Mixland+[®] TMTD masterbatch is a valuable secondary accelerator. In the vulcanization of CR with ETU, it is often used as a retarder.

It is suitable for NR, SBR, IR, BR, NBR, IIR and EPDM.

It readily disperses in rubbers. It liberates 13.3 % of sulfur at vulcanization temperatures. It is activated by aldehydeamine and guanidine accelerators. ZnO and stearic acid are required, whereas litharge tends to slow down vulcanization.

APPLICATIONS

Insulated electric wires, high-heat resistant products, tyres, tubes, cable, footwear, transparent articles, etc...

PACKAGING & STORAGE

- PE bags weight : 20 kg net
 - Standard CP3 pallet : 640 kg - Do not pile more than 2 pallets height
 - Shelf-life : **2 years** in its original packaging
- Store in a dry and cool place and away from direct sources of heat or sunlight.

SAFETY & TOXICITY

For detailed information, please refer to our Material Safety Data Sheet.

MIXLAND+[®] MASTERBATCH ALLOWS:

- Dust free products with a high level of filtration up to 100µ
- Tack free products at room temperature
- Lower Mooney viscosity, improving quality of dispersion
- Scrap rate reduction thanks to filtration
- Wider compatibility with elastomers

The information contained in this leaflet is based on tests carried out by our laboratories and data selected from the literature but shall in no event be held to constitute or imply any warranty or undertaking. No liability whatsoever can be accepted with regard to the handling, processing or use of the products concerned, which must in all cases be employed with regard to all relevant regulations and/or legislation in the country or countries concerned.

Issued 16 dated March 2022

TECHNICAL DATA SHEET

MLPC International

209, Avenue Charles Despiau – 40370 Rion des Landes - France
Tel.: +33 (0)5 58 57 02 78 – Contact : commercial@mlpc-intl.com
<http://www.mlpc-intl.com>

ARKEMA

DISCLAIMER FOR MEDICAL DEVICE POLICY

The product described in the brochure is not Medical grade designated for Medical Device applications.

Arkema general Medical Devices Policy

Arkema has implemented an internal Medical Policy regarding the use of Arkema products in Medical Devices applications that are in contact with the body or circulating bodily fluids. Arkema has designated Medical grades to be used for such Medical Device applications. Products that have not been designated as Medical grades are not authorized by Arkema for use in Medical Device applications that are in contact with the body or circulating bodily fluids. In addition, except for limited cases as determined by the Medical Device Policy, Arkema strictly prohibits the use of any Arkema products in Medical Device applications that are implanted in the body or in contact with bodily fluids or tissues for greater than 30 days. For any use of Arkema's product in Medical Device applications, please contact Arkema's sales network.